

⁷⁵As NMR study of the ternary iron arsenide BaFe₂As₂

Hideto Fukazawa^{1*}, Kenji Hirayama¹, Kenji Kondo¹, Takehiro Yamazaki¹, Yoh Kohori¹,
Nao Takeshita², Kiichi Miyazawa^{2,3}, Hijiri Kito², Hiroshi Eisaki², Akira Iyo²

¹*Department of Physics, Chiba University, Chiba 263-8522,*

²*Nanoelectronics Research Institute, National Institute of Advanced Industrial Science and Technology, Tsukuba 305-8562*

³*Department of Applied Electronics, Tokyo University of Science, Noda 278-8510*

(Received July 14, 2008)

We report ⁷⁵As nuclear magnetic resonance (NMR) measurements of the ternary iron arsenide BaFe₂As₂. ⁷⁵As-NMR spectra clearly revealed that magnetic transition occurs at around 131 K in our samples, which corresponds to the emergence of spin density wave. Temperature dependence of the internal magnetic field suggests that the transition is likely of the first order. The critical-slowness-down phenomenon in the spin-lattice relaxation rate $1/T_1$ is not pronounced in this material.

KEYWORDS: BaFe₂As₂, spin density wave, magnetic transition, nuclear magnetic resonance

The discovery of superconductivity in F-doped LaFeAsO with $T_c = 26$ K¹⁾ has accelerated the worldwide investigations of the related superconductors.^{2–13)} The common feature of these compounds is the possession of FeAs layer which is analogous to CuO₂ plane in high superconducting transition temperature (high T_c) cuprates. In addition, non-doped materials commonly exhibit spin density wave (SDW) or antiferromagnetic order with adjacent structural phase transition, which is also resemblance of the parent materials of high T_c cuprates. At present stage, the suppression of spin density wave (or antiferromagnetic order of localized moment) and/or the carrier control of non-doped materials seem to have a key role of the emergence of this new-class superconductivity. Recent nuclear magnetic resonance (NMR) studies of some of these superconducting oxypnictides strongly suggest that the superconductivity in the materials is unconventional one with nodes in the superconducting gap.^{4,5)}

Soon after the intensive investigations of the oxypnictides, oxygen-free iron pnictides BaFe₂As₂¹⁴⁾ and SrFe₂As₂¹⁵⁾ were proposed as a next candidate of the parent materials of superconductors with high T_c . The lattice parameter and the magnetic susceptibility of these materials were already reported about 25–30 years ago.^{16,17)} However, the deeper studies of the compounds have just started with consideration as the parent materials of superconductors. The crystal structure of these pnictides is the ThCr₂Si₂-type structure which is familiar in the heavy fermion systems. This structure possesses the similar FeAs layer to that realized in LaFeAsO. Moreover, both the materials exhibit the SDW anomalies at $T_{SDW} = 140$ K (BaFe₂As₂)^{14,18)} and $T_{SDW} = 205$ K (SrFe₂As₂).^{15,19)} It is important to notice that both the compounds exhibit structural phase transition from tetragonal one ($I4/mmm$) to orthorhombic one ($Fmmm$) simultaneously with the SDW anomaly.^{14,15,18,19)} The orders of these anomalies are reported as a second one for BaFe₂As₂¹⁴⁾ and a first one for SrFe₂As₂.^{15,19)} However, quite recent neutron diffraction

measurements of BaFe₂As₂ report hysteresis of tetragonal (220) peak between on-cooling sequence and on-warming sequence, which indicates the structural order at T_{SDW} is of the first order also in BaFe₂As₂.¹⁸⁾

The most striking feature of these compounds is that the SDW anomaly disappears and the superconductivity indeed sets in by hole doping, for example, K substitution for Ba²⁰⁾ or Sr.²¹⁾ In order to understand the superconductivity in these doped oxygen-free iron-based pnictides, it is also important to study the magnetic and the electronic properties of the parent materials. Especially the relation between the SDW instability and the superconductivity should be revealed by local-probe measurements in addition to bulk measurements. Hence, we performed ⁷⁵As-NMR measurements of BaFe₂As₂. ⁷⁵As-NMR spectra clearly exhibited the magnetic transition at around 131 K in our samples. Temperature T dependence of the internal magnetic field suggests that the transition is likely of the first order. The critical-slowness-down phenomenon in the spin-lattice relaxation rate $1/T_1$ is not pronounced in this material.

The polycrystalline BaFe₂As₂ was synthesized by the high temperature and high pressure method. The samples were confirmed as nearly single phase by x-ray diffraction. The standard four-probe resistivity measurement revealed the rapid decrease of the resistivity below 131 K, which corresponds to the SDW anomaly.²²⁾ The T_{SDW} of our samples is slightly lower than those reported by Rotter *et al.*¹⁴⁾ and Huang *et al.*¹⁸⁾ The samples were crushed into powder for the experiments. The NMR experiments of the ⁷⁵As nucleus ($I = 3/2$, $\gamma = 7.292$ MHz/T) have been carried out by using phase-coherent pulsed NMR spectrometers and a superconducting magnet. The NMR spectra were measured both by sweeping the applied fields at a constant resonance frequency and by sweeping the resonance frequency at a constant applied field. The origin of the Knight shift $K = 0$ of ⁷⁵As nucleus was determined by the ⁷⁵As NMR of GaAs.²³⁾ The $1/T_1$ was measured with the saturation recovery method.

In Fig. 1, we show the ⁷⁵As-NMR spectrum of

*E-mail address: hideto@nmr.s.chiba-u.ac.jp

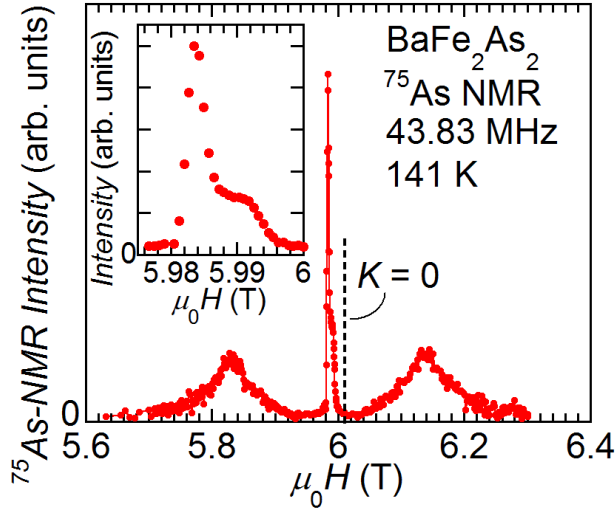


Fig. 1. (Color online) ^{75}As -NMR spectrum of BaFe_2As_2 at 141 K. Inset shows the center line of the enlarged spectrum between 5.975 and 6 T.

BaFe_2As_2 at 141 K in paramagnetic state. At this temperature, the crystal structure of BaFe_2As_2 is tetragonal.^{14,18)} The obtained spectrum is a powder pattern expected for weak electric quadrupole coupling.²⁴⁾ The nuclear-spin Hamiltonian with external magnetic field H_{ext} is given by $\mathcal{H} = -\gamma H_{\text{ext}} I_z + \frac{e^2 q Q}{4hI(2I-1)} (3I_z^2 - I(I+1))$, where h, e, q, eQ represent the Planck constant, the electric field gradient (EFG) and the nuclear quadrupole moment, respectively. The principal axis of the EFG is along the crystal c axis since As site above T_{SDW} has a local four-fold symmetry around the c axis.^{14,18)} Because of the same reason, the $\mathcal{H}$ above T_{SDW} does not contain the asymmetry parameter η of EFG. Sharp central peak was observed at around 5.98 T. In addition, rather broader satellite peaks were observed at around 5.83 and 6.13 T, which is due to the first-order perturbation effect of the electric quadrupole term against the Zeeman term in $\mathcal{H}$. From the difference of the resonance fields of the satellite lines, a nuclear quadrupole resonance frequency, $\nu_Q \equiv \frac{3e^2 q Q}{2hI(2I-1)}$, was estimated as 2.2 MHz. This value is about 4-5 times smaller than the values in iron-based oxypnictide superconductors.^{4,5,25,26)} This smaller value might suggest the low carrier density in the parent materials. Similar discussion was done in the nuclear quadrupole resonance of the oxygen-deficient iron oxypnictides²⁶⁾ and the high T_c cuprates.²⁷⁾

In the inset of Fig. 1, we show the center line of the enlarged spectrum between 5.975 and 6 T. This line shape is due to the second-order perturbation effect of the electric quadrupole term. The large peak at around 5.984 T and the edge-like structure at around 5.993 T originate from the resonance components perpendicular and 41.8°-inclined to the principal axis (crystal c axis) of the EFG, respectively. The enhancement of the perpendicular component, which is parallel to the crystal ab plane, is due to the partial orientation of the crystals in the H_{ext} . This suggests that the magnetic easy axis of BaFe_2As_2 is within the ab plane, which is consistent with the mag-

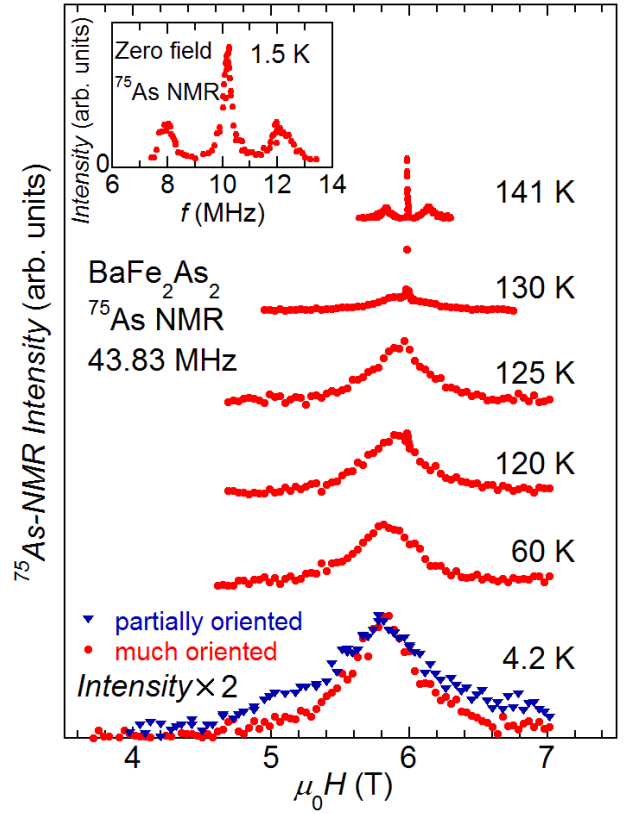


Fig. 2. (Color online) ^{75}As -NMR spectra of BaFe_2As_2 at various temperatures. Circles denote the spectrum with much oriented powders in external magnetic field and triangles the spectrum with partially oriented powders. Inset shows the zero-external-field ^{75}As -NMR spectrum at 1.5 K.

netic susceptibility parallel to the ab plane is about 1.5 times larger than that parallel to the c axis.²⁸⁾

In Fig. 2, we show the ^{75}As -NMR spectra of BaFe_2As_2 at various temperatures. The spectrum broadens below 130 K. This is clearly ascribable to the SDW magnetic ordering below $T_{\text{SDW}} = 131$ K. The quite weak signals from the center line observed in the paramagnetic state remains at around 6 T even in the magnetically ordered state. Since the signal intensity of this center peak below T_{SDW} becomes about 1/10 of that above T_{SDW} , we may speculate that the SDW ordered state and the paramagnetic state separately exist just below T_{SDW} , which implies that the order of the SDW anomaly in BaFe_2As_2 is of the first order. Note that the spectral broadening below T_{SDW} cannot be explained by the change of the ν_Q associated with the structural phase transition at T_{SDW} . Because the ν_Q is roughly inversely proportional to unit cell volume and the change of the unit cell volume associated with the SDW anomaly is at most 5%, the change of the ν_Q gives the spectral broadening of at most 0.02 T at half maximum of the intensity at 6 T. This is clearly much less than the experimental spectral broadening of 0.5 T at 120 K.

In Fig. 2, we also show two ^{75}As -NMR spectra at 4.2 K. One is obtained with much oriented powders and another is with partially oriented powders. The orientation of the micro crystals in powders was estimated from the fraction of the perpendicular component of the center line

spectrum in the paramagnetic state. Clear difference of the spectra was observed. The broader spectrum with partially oriented powders indicates the larger projection of the internal magnetic field H_{int} at As site along the H_{ext} . Since the c axis of each micro crystal in fully oriented powders is perpendicular to the H_{ext} , we deduce that the H_{int} at As site directs the crystal c axis. Recent neutron diffraction measurements revealed the ordered moment of $0.87\mu_B$ (Bohr magneton) at Fe site with the q vector of $(1, 0, 1)$ for the orthorhombic structure.¹⁸⁾ Indeed, the antiferromagnetic Fe ordered moment within the ab plane will make the H_{int} at As site parallel to the c axis because the As site locates at the top of the AsFe_4 pyramid. The sharper ^{75}As -NMR spectrum at 4.2 K is obtained in a condition that the H_{ext} and the H_{int} orient nearly perpendicular. Hence, the line width of the spectrum in Fig. 2 arises from the small angle distribution of the alignment, which is reduced from the bare H_{int} . However, the T dependence of the line width corresponds to that of the H_{int} . Assuming this ordered structure and the moment along the a or the b axis, we evaluated that the dipole field at As site is approximately 0.3 T. This is less than the H_{int} estimated from the spectral width of the ^{75}As -NMR. The contribution of conduction electrons is involved in the actual H_{int} , though the direction of the H_{int} depends on that of the ordered moments and the ordered structure.

In the inset of Fig. 2, we show zero-field ^{75}As -NMR spectrum at 1.5 K. These narrow center line and broad satellites indicate that the H_{int} at As site had a magnitude of about 1.3 T and its orientation is the maximum EFG direction at As site (c axis). The narrow lines suggest that the magnetically ordered state is basically formed with the commensurate q vector, which is consistent with neutron scattering measurements.¹⁸⁾ The origin of the broader satellites is probably due to the slight distribution of the EFG in the orthorhombic structure through the first order structural phase transition. Note that the broadening of the NMR spectra in the H_{ext} is due to the distribution of the projection component of the H_{int} along the H_{ext} . Quite recent ^{75}As -NMR measurements of single crystals and polycrystals of BaFe_2As_2 by Baek *et al.* apparently revealed that the magnetically ordered state is incommensurate.²⁹⁾ However, our zero-field ^{75}As -NMR spectrum indicates that the magnetically ordered state is commensurate.

In Fig. 3, we show the T dependence of the full width at half maximum $FWHM$ and quarter maximum $FWQM$ of the ^{75}As -NMR spectra with much oriented powders. As already described above, spectral width can be considered as the rough measure of the distribution of the internal magnetic field H_{int} at As site. The $FWHM$ are nearly T independent and the $FWQM$ slightly decreases on warming between 4.2 and 130 K. Then they abruptly decrease from finite field toward zero field at around T_{SDW} . This discontinuous tendency of the magnetic internal field at T_{SDW} can be interpreted that the order of the SDW anomaly is likely of the first one.

In the inset of Fig. 3, we show the Knight shift K_{ab} along the ab plane of ^{75}As -NMR of BaFe_2As_2 versus χ_{ab} , magnetic susceptibility parallel to the ab plane

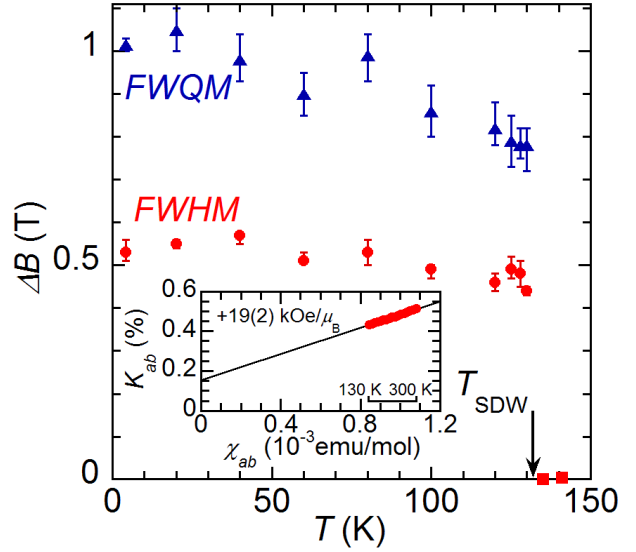


Fig. 3. (Color online) T dependence of the full width at half maximum $FWHM$ (closed circle) and quarter maximum $FWQM$ (closed triangle) of the ^{75}As -NMR spectra of BaFe_2As_2 . Closed squares denote the $FWHM$ of the center line in the paramagnetic state. Inset shows Knight shift K_{ab} along the ab plane of ^{75}As -NMR of BaFe_2As_2 versus the magnetic susceptibility χ_{ab} .²⁸⁾

above T_{SDW} . The K_{ab} above T_{SDW} was obtained from the perpendicular component of the center line of the frequency-swept spectra at a constant applied field of 5.98 T. The second order quadrupole effect was taken into account to obtain K_{ab} .²⁴⁾ The data of χ_{ab} was taken from ref. 28. The hyperfine coupling constant A_{ab} parallel to the ab plane was evaluated from the Knight shift at As site parallel to the ab plane and the magnetic susceptibility parallel to the ab plane by assuming the following formulae, $K_{ab}(T) = \frac{A_{ab}^d}{N_A \mu_B} \chi_{ab}^d(T) + \frac{A_{ab0}}{N_A \mu_B} \chi_{ab0}$ ($\chi_{ab}(T) = \chi_{ab}^d(T) + \chi_{ab0}$). Here, N_A represents Avogadro number. The evaluated hyperfine coupling constant A_{ab}^d originating from the coupling between ^{75}As nuclear spin and $3d$ conduction electron of Fe is $+19(2)$ kOe/ μ_B . This is the same magnitude of the coupling constant as that reported for the ^{75}As -NMR of $\text{LaFeAsO}_{0.9}\text{F}_{0.1}$.²⁵⁾

In Fig. 4, we show T dependence of $1/T_1$ of ^{75}As of BaFe_2As_2 . We obtained T_1 at a fixed frequency of 43.83 MHz with the external field of 5.75–5.98 T in the T range of 4.2–131 K and at a fixed field of 5.98 T with the frequency of 43.83–43.87 T in the T range of 131–300 K. The nuclear magnetization recovery curve was fitted by a following double exponential function as expected for the center line of the spectrum of the nuclear spin $I = 3/2$ of the ^{75}As nucleus,³⁰⁾ $1 - \frac{m(t)}{m_0} = 0.1 \exp\left(-\frac{t}{T_1}\right) + 0.9 \exp\left(-\frac{6t}{T_1}\right)$, where $m(t)$ and m_0 are nuclear magnetizations after time t and enough time from the NMR saturation pulse. In the inset of Fig. 4, we show typical recovery curve obtained at 266 K. Clearly the data are well fitted to the above ideal curve with a single T_1 component. We used this formula even below T_{SDW} , where the recovery curve should be more compli-

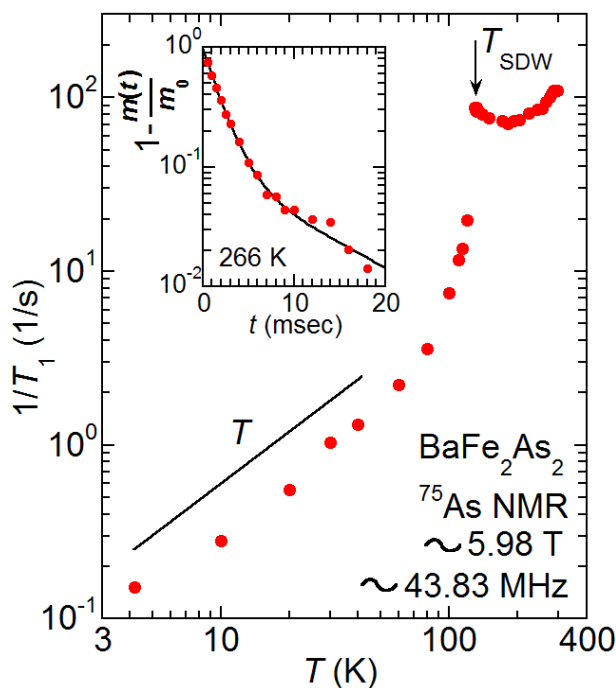


Fig. 4. (Color online) T dependence of spin-lattice relaxation rate $1/T_1$ of ^{75}As of BaFe_2As_2 . The inset shows the typical recovery curve obtained at 266 K.

cated and the concrete form cannot be derived. However, the analysis below T_{SDW} yielded good fitting with a single T_1 component. $1/T_1$ exhibits rapid decrease between 180 and 300 K. The slope of the $1/T_1$ is greater than T linear dependence. This anomalous T dependence is quite different from that reported in the related parent compound LaFeAsO where $1/T_1$ of ^{139}La is nearly T independent sufficiently above T_{SDW} .⁴⁾ Below about 180 K, $1/T_1$ exhibits gradual increase and sudden decrease below 131 K = T_{SDW} . Note that the critical-slowing-down phenomenon in this material is not pronounced, which is contrast to the case of LaFeAsO in which the phenomenon was more clearly observed in $1/T_1$ of ^{139}La .⁴⁾ The steep decrease of $1/T_1$ below T_{SDW} is probably due to a gap formation of the SDW at part of the Fermi surface. $1/T_1$ below about 100 K is nearly proportional to T . This is attributable to the relaxation due to the remaining conduction electron at the Fermi level even below T_{SDW} .

In BaFe_2As_2 and its isomorph SrFe_2As_2 , the magnetic anomaly and the structural anomaly coincide with each other at T_{SDW} .^{14, 15, 18, 19)} This is in contrast to the case in the related compound LaFeAsO in which the magnetic anomaly and the structural anomaly occur with the separation of about 10 K.⁴⁾ Moreover, the present results of ^{75}As NMR measurements of BaFe_2As_2 support that the magnetic transition at T_{SDW} is likely of the first order. Further investigation of the relation between the coincidence/separation of the magnetic anomaly and the structural anomaly and the order of the phase transition in the parent materials is quite important to understand the superconductivity adjacent to the magnetic and the structural anomalies in the iron-based oxypnictides/pnictides.

In summary, we performed ^{75}As NMR measurements of the ternary iron arsenide BaFe_2As_2 which is a parent compound of new-class iron-based superconductors. ^{75}As -NMR spectra clearly revealed that magnetic transition occurs at around 131 K in our samples, which corresponds to the emergence of SDW. T dependence of the H_{int} suggests that the transition is likely of the first order. However, it is still an open question whether this transition is of the first order or of the second one. The detailed specific heat measurements will answer this question and is strongly required. The critical-slowing-down phenomenon in $1/T_1$ is not pronounced in this compound. Finally we comment about the pressure effect on these iron-based oxypnictides/pnictides. Not only doping study but also recent pressure study of the oxypnictides revealed that the pressure much affects these materials in the electronic states in the broad pressure range up to about 30 GPa.^{3, 8)} This indicates that the subsequent NMR/NQR studies of iron-based oxypnictides/pnictides under high pressure requires such high pressure of 10 GPa class. Recent development of high pressure NMR/NQR technique by the authors' group^{31, 32)} will help for giving further insights into the understanding of these fascinating iron-based oxypnictides/pnictides.

This work is supported by a Grant-in-Aid for Scientific Research from the MEXT.

- 1) Y. Kamihara *et al.*: J. Am. Chem. Soc. **130** (2008) 3296.
- 2) H. Kito *et al.*: J. Phys. Soc. Jpn. **77** (2008) 063707.
- 3) N. Takeshita *et al.*: J. Phys. Soc. Jpn. **77** (2008) 075003.
- 4) Y. Nakai *et al.*: J. Phys. Soc. Jpn. **77** (2008) 073701.
- 5) K. Matano *et al.*: to be published in J. Phys. Soc. Jpn. **77** (2008).
- 6) S. Ishibashi *et al.*: J. Phys. Soc. Jpn. **77** (2008) 053709.
- 7) T. Sato *et al.*: J. Phys. Soc. Jpn. **77** (2008) 063708.
- 8) H. Takahashi *et al.*: Nature **453** (2008) 376.
- 9) Z. A. Ren *et al.*: Chin. Physics. Lett. **25** (2008) 2215.
- 10) G. F. Chen *et al.*: Chin. Physics. Lett. **25** (2008) 2235.
- 11) Z. A. Ren *et al.*: Euro. Phys. Lett. **82** (2008) 57002.
- 12) X. H. Chen *et al.*: Nature **453** (2008) 761.
- 13) C. Cruz *et al.*: Nature **453** (2008) 899.
- 14) M. Rotter *et al.*: arXiv:0805.4021v1.
- 15) C. Krellner *et al.*: arXiv: 0806.1043v1.
- 16) M. Pfisterer and G. Nagorsen: Z. Naturforsch. B: Chem. Sci. **35** (1980) 703.
- 17) M. Pfisterer and G. Nagorsen: Z. Naturforsch. B: Chem. Sci. **38** (1983) 811.
- 18) Q. Huang *et al.*: arXiv:0806.2776v1.
- 19) J.-Q. Yan *et al.*: arXiv:0806.2711v1.
- 20) M. Rotter *et al.*: arXiv:0805.4630v1.
- 21) G. F. Chen *et al.*: arXiv:0806.1209v1.
- 22) Y. Tomioka: private communications.
- 23) T. J. Bastow: J. Phys.: Condens. Matter **11** (1999) 569.
- 24) G. C. Carter *et al.*: *Metallic Shifts in NMR* (Pergamon Press, Oxford, New York, Toronto, Sydney, Paris, Frankfurt, 1977) Chap. 2&6.
- 25) H.-J. Grafe *et al.*: arXiv:0805.2595v2.
- 26) H. Mukuda *et al.*: arXiv:0806.3238v1.
- 27) G.-q. Zheng *et al.*: Physica C **260** (1996) 197.
- 28) X. F. Wang *et al.*: arXiv:0806.2452v1.
- 29) S.-H. Baek *et al.*: arXiv: 0807.1084v2.
- 30) W. W. Simmons *et al.*: Rhy. Rev. **127** (1962) 1168.
- 31) H. Fukazawa *et al.*: Rev. Sci. Instrum. **78** (2007) 015106.
- 32) K. Hirayama *et al.*: J. Phys. Soc. Jpn. **77** (2008) 075001.